

Observation of acoustic avoided crossing in an optical fiber taper

Jean-Charles Beugnot¹, Raja Ahmad², Martin Rochette², Joël Cabrel Tchahame¹, Kien Phan Huy¹, Vincent Laude¹, Hervé Maillotte¹, and Thibaut Sylvestre¹

1. FEMTO-ST Institute, CNRS UMR 6174, Université de Franche-Comté, Besançon, France

2. Department of Electrical and Computer Engineering, McGill University, Montreal (QC), Canada

The rich and complex dynamics of light and sound interactions in tiny optical waveguides has recently gained much interest because of their experimental realization in emerging key areas of photonics [1,2]. For instance, we recently demonstrated the generation of a new class of surface acoustic waves in a subwavelength-diameter silica optical fiber taper [3]. In such thin silica wires, boundary conditions induce a strong coupling of shear and longitudinal displacements, resulting in a much richer dynamics of light interaction with hybrid acoustic phonons. Avoided crossings can thus occur due the strong photon-phonon coupling and to the fact that these acoustic modes are no longer orthogonal and thus can interact. This interaction can be sufficiently strong enough for certain acoustic frequencies to be forbidden at some anti-crossing points, giving rise to new characteristics such as Brillouin frequency gap.

In this work, we report the first observation of avoided crossing for acoustic waves in a subwavelength optical fiber. This was achieved in a highly nonlinear polymer-coated chalcogenide (As_2Se_3) optical microwire through a detailed investigation of the backward Brillouin scattering based on a heterodyne detection [4]. We show in particular that the Brillouin frequency shift no longer depends linearly on the pump wavelength, however it exhibits a large frequency gap due to avoided crossing. By tuning the laser wavelength, it is actually possible to vary the acoustic wave vector through the phase-matching condition and to observe the effect of anti-crossing.

The PMMA- As_2Se_3 microwire is schematically shown in Fig. 1(a). It has a core diameter of $1.08 \mu\text{m}$ and a length of 13 cm. The microwire is butt-coupled to single-mode fibers and permanently bonded with UV-epoxy. As a pump laser, we used a narrow-linewidth DFB laser tunable from 1526 nm to 1613 nm with an output power of 10 mW. Figure 1(b) shows the output experimental Brillouin spectrum as a function of the laser wavelength. At a wavelength of 1600 nm, we clearly observe the Brillouin frequency gap due to acoustic avoided crossing. The Brillouin spectrum simultaneously exhibits two detuned acoustic resonances for this specific wavelength. Numerical calculations of the Brillouin spectrum using the elastodynamics equation subject to an *electrostrictive* force presented in the previous work [4] are in good agreement with experimental results.

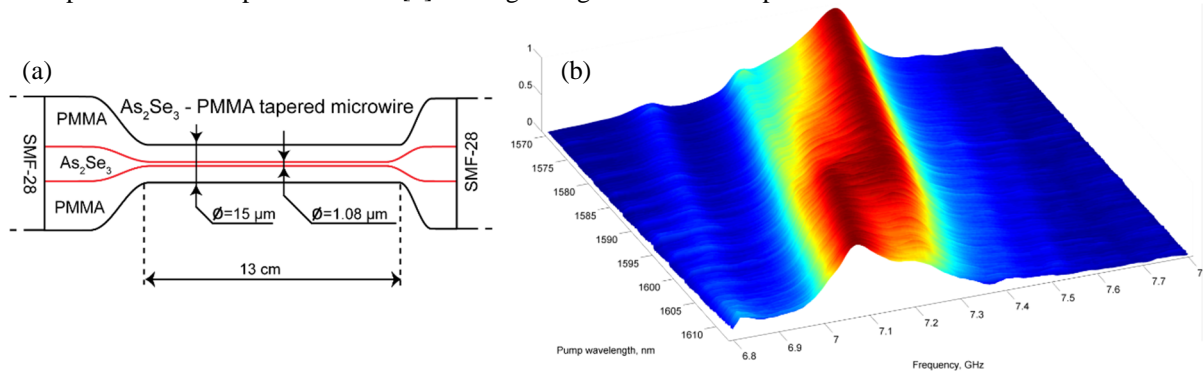


Fig. 1 (a) Scheme of the hybrid As_2Se_3 -PMMA optical microwire used to observe avoided crossing effects. (b) Experimental Brillouin backscattering spectrum as a function of pump wavelength showing the nonlinear frequency gap due to avoided crossing at a pump wavelength of 1600 nm.

To conclude, we have shown the existence of acoustic avoided crossing by mapping the phonons dispersion in a sub-wavelength diameter chalcogenide microwire. These findings can help for further understanding of light-sound interactions in subwavelength nanoscale waveguides.

This work was supported by the Labex ACTION (ANR-11-LABX-0001-01) and the OASIS ANR project.

References

- [1] H. Shin, W. Qiu, R. Jarecki, J. A. Cox, R. H. Olsson, A. Starbuck, Z. Wang and P. T. Rakich, "Tailorable stimulated Brillouin scattering in nanoscale silicon waveguides," *Nat. Comm.* **4**, (2013).
- [2] R. Pant, E. Li, C. G. Poulton, D-Y. Choi, S. Madden, B. Luther-Davies and B. J. Eggleton, "On-chip stimulated Brillouin scattering," *Opt. Lett.* **38**, 305–307 (2013).
- [3] J-C. Beugnot, S. Lebrun, G. Pauliat, H. Maillotte, V. Laude, V. and T. Sylvestre, "Brillouin light scattering from surface acoustic waves in a subwavelength-diameter optical fibre," *Nat. Comm.* **5** (2014).
- [4] J-C. Beugnot, R. Ahmad, M. Rochette, V. Laude, H. Maillotte and T. Sylvestre, "Reduction and control of stimulated Brillouin scattering in polymer-coated chalcogenide optical microwires," *Opt. Lett.* **39**, 482–485 (2014).